Study of The Influence Of Doping Concentration And Temperature On The Offset Voltage Of Piezoresistive Pressure Sensor

Mohamed Ras lain and Abdelhafid chaabi
Département d'électronique, Faculté des sciences de l'ingénieur, Université Mentouri, Constantine
Algeria E-mail : raslain05@yahoo.fr

Abstract- **Based on the phenomena of displacement of the majority carriers in silicon and based on the assumption that each piezoresistor of a silicon pressur sensor has its own temperature coefficients (TCRs of the first and second order), this study gives an explanation on the existence of the offset volage in the piezoresitif pressure sensors and its thermal behaviour.**
Using different models of majority carriers mobility in silicon, this paper presents a new formula for the first and the second temperature coefficient α and β in function of doping concentration N (cm^{-3}).On the other hand, this new presentation enable us to present the thermal behaviour of piezoresistive pressure sensors in function of two parameters namely the doping concentration N (cm^{-3}) and temperature T (°C) then we report the effect of the temperature on the offset voltage

I. INTRODUCTION

A major problem associated with piezoresistive pressure sensors is their cross to temperature. The influence of temperature is manifested as a change in the span and offset sensor output, silicon resistor is realized by microelectronic techniques using ion implantation technique and the study of its thermal behaviour presents fundamental interest. In this work, which is closely related to[1], this last studied the effects of doping concentration on the first and second order temperature coefficients of resistance (TCRs) ,he has used three models of majority carries mobility in silicon and in our work we added another model of mobility [2] we present a new formula of theses two thermal coefficients, α and β of a silicon resistor, where we present their relationship only in function of the doping concentration N(cm^{-3}).Finally we present an analytical expression of resistance of the silicon resistor and we have established the expression of the thermal variations of the offset voltage.

II. INFLUENCE OF TEMPERATURE

At temperature T, the thermal variation of resistance of silicon can be evaluated by the following expression [3]

$$R(T) = R(T_0)(1 + \alpha(T - T_0) + \beta(T - T_0)^2) \quad (1)$$

Where $R(T_0)$ is the value of the resistance at the reference temperature T_0 ; α and β are the temperature coefficients of the first and second power of T respectively.
Many good review articles [4-5] use theses two coefficients α and β . In particular the first coefficient has been studied by Bullis *et al.* [6], he has found it in experiment and presents the influence of doping concentration while the other study of these two coefficients have been reported by [1] , where he used three models of mobility for presenting the influence of doping concentration on these two coefficients.

III. EFFECT OF DOPING ON THE TWO TEMPERATURE COEFFICIENTS

The resistance value of a semiconductor bar is:

$$R = \rho L / S \quad (2)$$

Where L, S and ρ are its length, surface and resistivity, respectively. By neglecting the dimensional variations compared to those of resistivity, the thermal variations of resistance is [1] :

$$\Delta R / R_0 = \Delta\rho / \rho_0 \quad (3)$$

Where R_0 and ρ_0 are the values of resistance and resistivity at temperature T_0 respectively. The comparison of (2) and (3) leads to:

$$\Delta\rho / \rho_0(T) = \alpha(T - T_0) + \beta(T - T_0)^2 \quad (4)$$

However in the case of a P-doping with N concentration, the resistivity can be approximated by :

$$\rho \approx \frac{1}{(q\mu_p N)} \quad (5)$$

Where q and μ_P are elementary charge and the holes mobility respectively.
We have used different hole mobility models [2-7-8-9] , by introducing equations giving μ_P as a function of N_A, we obtain , for each value of concentration , a coefficient for T and another for T^2 .By identification with (4), coefficient α and β can be easily found. This method has been repeated

for different concentrations between 10^{17} cm^{-3} and 10^{20} cm^{-3} [1] .

Using these four models of majority carries mobility in silicon [2-7-8-9] , we present the evolution of the first and second temperature coefficients as well as the relationship existing between each of α and β and the doping concentration N . This definition allows us to present the relationship between the resistance R(T) and the two parameters T and N. By using the values of α and β in interpolation program, we obtain equations relating those two coefficients of temperature in function of the doping concentration *N* and we have found a 4th degree logarithmic regression function.

The expressions giving these variations are as follow:

$$\alpha(N) = A + B\log(N) + C\log^2(N) + D\log^3(N) + E\log^4(N) \quad (6)$$

$$\beta(N) = A' + B'\log(N) + C'\log^2(N) + D'\log^3(N) + E'\log^4(N) \quad (7)$$

Where A, B, C, D, E and A', B', C', D', E' are constants of the function of α and β and N is the doping concentration of the silicon resistor.

We have reported in the table I and II the 5 constants of α and β using the four models.

We are now able within this model represent the variations of α and β in function of the doping concentration N; and the results are shown in the figures 1 and 2.

A. For α (fig. 1):

- Between 3×10^{18} cm^{-3} and 4×10^{18} cm^{-3} curve (iv) has a minimal value approximately 480 ppm/°C.
- Curves (ii), (iii) and (iv) are relatively close to one another (except curve (iv) for doping higher than 2×10^{19} cm^{3}).
- Until 2×10^{19} cm^{-3} the values of α for the curve (i) are higher than the values obtained for the three curves (ii),(iii) and (iv) and its value becomes minimal from 4×10^{19} cm^{-3} .
- The existence of a value minimal of α is remarkable in the three models (ii),(iii) and (iv).

B. For β (fig. 2):

- Curves (i), (iv) and (ii) have a possibility of passing by the zero, so in this case $\beta = 0$.
-Curves (ii), (iii) and (iv) show a monotonous decrease until a doping concentration of approximately 10^{19} cm^{-3} with doping.
- The curve (iii) takes high values compared to the other curves.

Comparing our results with those obtained in [1], we notice the following points:

-The first coefficient α is identical.

-We have obtaining the same variation of β using the three models of mobility, except there is a shift of value using a model of Klaassen and Dorckel.

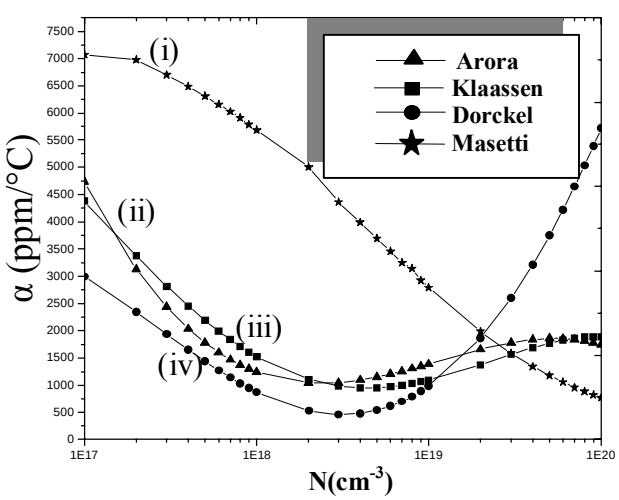

Fig. 1: Variations of α in function of the doping concentration

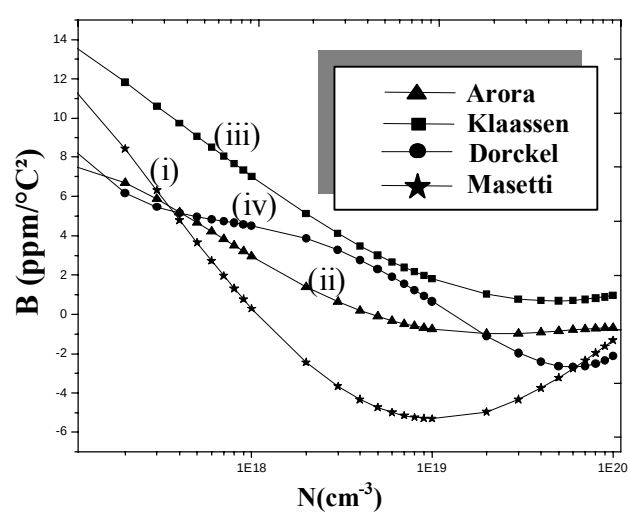

Fig. 2: Variations of β in function of the doping concentration N.

TABLE. I

Constants of α / Models of mobility	A	B	C	D	E
Arora	-705288.03348	386396.02481	-49263.53998	2384.2094	-39.93215
Klaassen	-2.00231E7	4.44985E6	-369115.63611	13550.44074	-185.808
Dorckel and Leturcq	-1.20717E7	2.54514E6	-199158.06738	6847.66465	-87.14671
Masetti	9.6924E6	-2.2322E6	192222.54016	-7326.19557	104.20675

TABLE. II

Constants of β / Models of mobility	A'	B'	C'	D'	E'
Arora	-53982.9634	11605.05634	-932.6115	33.21372	-0.4424
Klaassen	-12589.238008	2644.78304	-205.54902	7.00987	-0.08853
Dorckel and Leturcq	140978.75194	-30622.58872	2492.26207	-90.06064	1.21907
Masetti	-68178.19235	14731.11556	-1187.46977	42.33521	-0.56337

Introducing the two formulas (6) and (7) in expression (1) we represent a new formula for *R (T):*

$$R(T) = R(T_0)\left[\, 1 + (A + B\log(N) + \ldots + E\log^4(N))(T - T_0) + (A' + B'\log(N) + \ldots + E'\log^4(N))(T - T_0)^2 \,\right] \quad (8)$$

So, the relative resistance is given by this equation:

$$\frac{R(T) - R(T_0)}{R(T_0)} = (A + B\log(N) + \ldots + E\log^4)(T - T_0) + (A' + B'\log(N) + \ldots + E'\log^4(N))(T - T_0)^2 \quad (9)$$

IV. OFFSET VOLTAGE

Connecting the four piezoresistors in a Wheatstone bridge (figure 3)

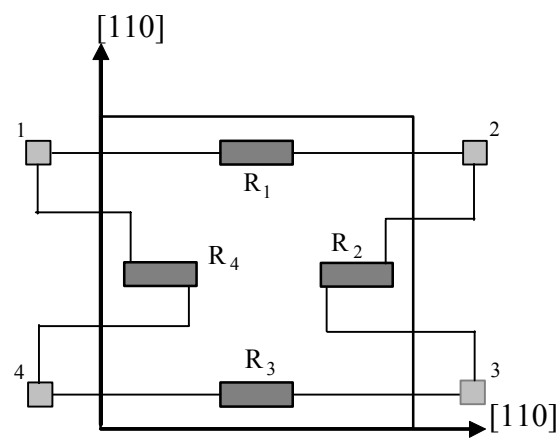

Fig 3 **:** Implantation of the piezoresistors on the top of the silicon membrane

The thermal variation of the output voltage is:

$$\Delta(T) = V_0\left[\frac{R_1(T_0)R_2(T_0)}{(R_1(T_0)+R_2(T_0))^2}\left[(\alpha_1-\alpha_2)T+(\beta_1-\beta_2)T^2\right]\right] - V_0\left[\frac{R_3(T_0)R_4(T_0)}{(R_3(T_0)+R_4(T_0))^2}\left[(\alpha_3-\alpha_4)T+(\beta_3-\beta_4)T^2\right]\right] \quad (10)$$

Where:

- V_0 is the supply voltage of the Wheatstone bridge.
- α and β are temperature coefficients (i=1, 2, 3, 4).
- $R_i(T_0)$ (i=1, 2, 3, 4) are the value of the piezoresistor at the reference temperature.

We can take [4]:

$$\frac{R_1(T_0)R_2(T_0)}{(R_1(T_0)+R_2(T_0))^2} = \frac{R_3(T_0)R_4(T_0)}{(R_3(T_0)+R_4(T_0))^2} \approx 0.25 \quad (11)$$

Introducing the expressions (6) and (7) of α and β in the expression of offset voltage (10) we obtained it variation directly as function of the doping concentration N and in this case we can see it influence in the offset voltage, in our study we take two values $N = 2\times10^{18}\,cm^{-3}$ and $N = 4\times10^{18}\,cm^{-3}$

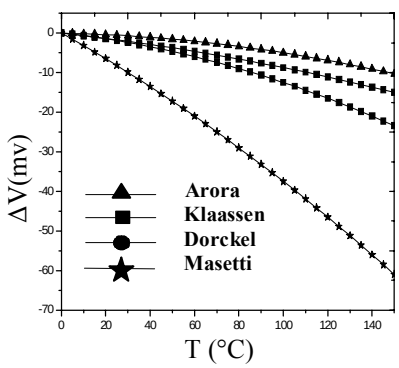

1- $R_1 \neq R_2=R_3=R_4$

Fig. 4 Variations of ΔV in function of temperature using the cas where one of four piezoresistors (R_1) different from the others and $N = 2\times10^{18}\,cm^{-3}$.

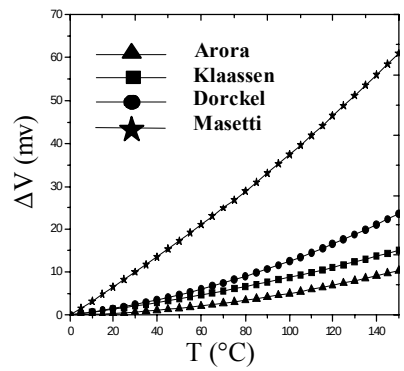

2- $R_3 \neq R_1=R_2=R_4$

Fig. 5 Variations of ΔV in function of temperature using the cas where one of four piezoresistors (R_3) different from the others and $N = 2\times10^{18}\,cm^{-3}$.

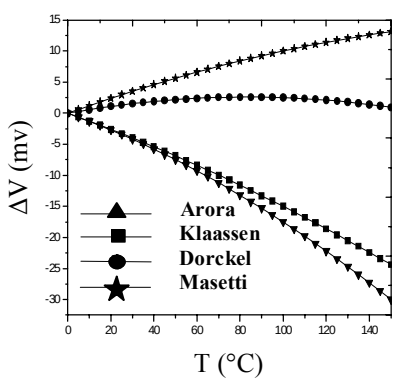

1- $R_1 \neq R_2=R_3=R_4$

Fig. 6 Variations of ΔV in function of temperature using the cas where one of four piezoresistors (R_1) different from the others and $N = 4\times10^{18}\,cm^{-3}$.

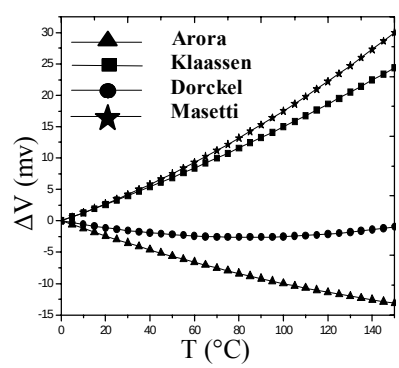

2- $R_3 \neq R_1=R_2=R_4$

Figs. 7 Variations of ΔV in function of temperature using the cas where one of four piezoresistors (R_3) different from the others and $N = 4\times10^{18}\,cm^{-3}$.

Figures (4),(5),(6) and figure (7) shows us a non linear variation of the offset voltage, thus it's very remarkable that in the case of $N = 2\times10^{18}\,cm^{-3}$ the thermal behaviour of the offset voltage varies approximately from 0 to 70 mv and from 0 to 30 mv for the doping $N = 4\times10^{18}\,cm^{-3}$.

V. CONCLUSION

The theoretical aspects of the thermal variations of the offset voltage of silicon piezoresitive pressure sensors have been developed by assuming that there exists a difference in the doping concentration of the four piezoresistors constituting the Wheatstone bridge. The numerical model of α and β obtained in this work allowed us to obtain a new formula for these two coefficients of temperature. Then using the interpolation program we obtained the variations of these two coefficients in function of the doping concentration *N* only.
With these formulas we can obtain usually a thermal variation of the offset voltage only in function of two parameters, temperature T and doping N. This new method for driving α, β in function of N, ΔV in function of N and T should be of interest to people working in the field of sensors where we they can easily extract the numerical values of the two coefficients α and β and use them in the formula of the offset voltage.

REFERENCES

1. A. Boukabache, P. Pons, "Doping effects on thermal behaviour of silicon resistor," electronics letters 28TH march 2002 vol. 38 N. 7, pp. 342-343.

2. G. Masetti, M. Severi, and S. Solmi, "Modeling of carrier concentration in Arsenic-, Phosphorus-, and Boron-Doped Silicon," IEEE Transactions on electron devices, 1983, Vol. ED-30, NO 7, pp.764-769

3. Shirousu, S. Kimijima, S.Sato," Offset temperature drift of silicon pressure sensor," Proc. 2nd sensor symp, Tsukuba. Japan. 1982, PP. 249-256.

4. A.Boukabache, P.Pons, G.Blasquez, Z.Dibi," Characterisation and modelling of the mismatch of TCRs and their effects on the drift of the offset voltage of piezoresistive pressure sensors," Sensors and actuators A, 2000, 84, pp 292-296

5. V. Stankevic, C. Simkevicius," Application of aluminium films as temperature sensors for the compensation of output thermal shift of silicon piezoresistive pressure sensors," Sensors and Actuators A, 1998, 71, pp 161-166.

6.W.M.Bullis,F.H.Brewere,C.D.Kolstad,L.J.SWARTZEN DRUBER," Temperature coefficient or resistivity of Silicon and Germanium near room temperature" Solid-State Electronics, 1968, Vol. 11, pp. 639-646.

7. D.B.M.Klaassen," A unified mobility model for device simulation –I. Model equations and concentration dependence," Solid-State electronics, 1992, Vol 35, n° 7 pp. 953-959.

8. N.D.Arora, J.R Hauser, and D.J. Roulston " Electron and hole motilities in silicon as a function of concentration and temperature" IEEE Trans. Electron devices, 1982, ED-29 (2), pp. 292-295

9. J.M. Dorckel, P.Leturcq," Carrier motilities in Silicon semi-empirically related to temperature doping and injection level," Solid-State electronics, 1981, Vol.24, pp. 821-825